

**OFFICE OF NAVAL RESEARCH**

**TECHNICAL REPORT**

**FOR**

**Grant N00014 91 J 1035**

**R & T Code 413302S - Robert Nowak**

**Technical Report No. 34**

**Energetics of Electron Transfer at the Nanocrystalline Titanium Dioxide  
Semiconductor/Aqueous Solution Interface: pH Invariance of the Metal Based  
Formal Potential of a Representative Surface Attached Dye Couple**

**Prepared for publication in *J. Phys. Chem.*, October, 1996.**

**Susan G. Yan and Joseph T. Hupp\***

**Department of Chemistry and Materials Research Center  
Northwestern University  
Evanston, IL 60208**

**DISTRIBUTION STATEMENT A**

**Approved for public release:  
Distribution Unlimited**

**DTIC QUALITY INSPECTED 4**

**Reproduction in whole, or in part, is permitted for any purpose of the United States Government.**

**19961022 097**

# REPORT DOCUMENTATION PAGE

Form Approved  
GSA No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)

2. REPORT DATE

October 10, 1996

3. REPORT TYPE AND DATES COVERED

Technical Report, 34

4. TITLE AND SUBTITLE Energetics of Electron Transfer at the Nanocrystalline Titanium Dioxide Semiconductor/Aqueous Solution Interface: pH Invariance of the Metal Based Formal Potential of a Representative Surface Attached Dye Couple

5. FUNDING NUMBERS

G.N00014-91-J-1035

6. AUTHOR(S)

Susan G. Yan and Joseph T. Hupp

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)

Department of Chemistry  
Northwestern University  
2145 Sheridan Road  
Evanston, Illinois 60208-3113

8. PERFORMING ORGANIZATION REPORT NUMBER

34

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)

Office of Naval Research  
Chemistry Division  
800 North Quincy Avenue  
Arlington, VA 22217-500

10. SPONSORING/MONITORING AGENCY REPORT NUMBER

11. SUPPLEMENTARY NOTES

Prepared for publication in J. Phys. Chem., October, 1996.

12a. DISTRIBUTION/AVAILABILITY STATEMENT

Reproduction in whole, or in part, is permitted for any purpose of the United States Government.

12b. DISTRIBUTION CODE

13. ABSTRACT (Maximum 200 words)

Mediator-based spectroelectrochemical assessment of the metal-centered formal potential ( $E_f^{Ru}$ ) of a representative inorganic dye,  $Ru(4,4'-(CH_2PO_3)-2,2'$ -bipyridine) $_3^{10+}$ , bound to a nanocrystalline titanium dioxide film shows that the potential is insensitive to changes in solution pH, despite significant shifts in the conduction band edge energy ( $E_{CB}$ ) of the underlying semiconductor electrode in response to the same environmental perturbations. The observations are important in the context of recent work showing that back electron reactivity for the same semiconductor/dye combination is pH independent over a 19 pH unit range, despite apparent changes in back reaction driving force of greater than 1.2 eV over the same interval (Yan, S.; Hupp, J. T. *J. Phys. Chem.* 1996, 100, 6867). In particular, the spectroelectrochemical findings serve to rule out a suggested alternative interpretation of the unusual kinetic effects whereby the crucial energy difference quantity,  $E_{CB} - E_f^{Ru}$ , remains fixed because of compensating changes in the dye potential with pH.

14. SUBJECT TERMS

15. NUMBER OF PAGES

15

16. PRICE CODE

UL

17. SECURITY CLASSIFICATION OF REPORT

unclassified

18. SECURITY CLASSIFICATION OF THIS PAGE

unclassified

19. SECURITY CLASSIFICATION OF ABSTRACT

unclassified


20. LIMITATION OF ABSTRACT

UL

## Introduction

Inorganic dye sensitization of wide band gap semiconductors has attracted tremendous recent attention because of the possibility of relatively efficient visible light to electrical energy conversion in photoelectrochemical cells that employ these assemblies.<sup>1</sup> The assemblies are also of interest because of their ability to offer insight into the fundamental kinetics and dynamics of fast interfacial redox processes.<sup>2</sup> Recently we reported on the kinetics for back electron transfer from  $\text{TiO}_2$  to a hexaphosphonated form of ruthenium tris bipyridine, following light-induced forward electron injection from a charge-transfer excited state of the metal complex.<sup>3</sup>

Hexaphosphonation served to facilitate strong surface attachment thereby permitting the reaction to be examined over an extremely wide pH range.<sup>3,4</sup> The surprising finding was that the back ET kinetics were pH independent,<sup>3</sup> despite the known Nernstian dependence of the  $\text{TiO}_2$  conduction band edge energy ( $E_{\text{CB}}$ ) on solution pH.<sup>5</sup> Indeed, over the pH range examined the nominal strength of  $\text{TiO}_2$  as a reductant varied by more than 1.2 eV.<sup>3</sup> The striking decoupling of the ET kinetics from the pH-variable energetics was speculatively interpreted in terms of a sequential electron transfer/proton transfer process where: a) the isolated electron transfer event (pH independent) defined the rate-determining dynamics, but b) the combined processes (pH dependent) determined the overall reaction energetics. Supporting evidence for the interpretation was garnered from quartz crystal microbalance experiments which independently showed that proton transfer (intercalation) accompanies both electrochemical and photochemical addition of electrons to the titanium dioxide conduction band or nearby surface states.<sup>6</sup>

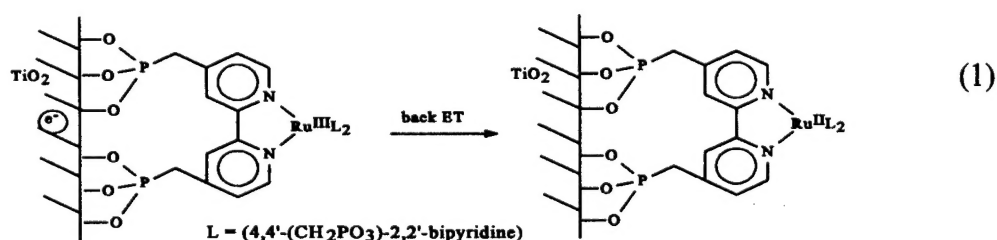

An interesting alternative interpretation of the pH-independent kinetics is that the formal potential for the ruthenium dye ( $E_f^{\text{Ru}}$ ) acquires a pH dependence upon confinement to the semiconductor surface.<sup>7</sup> If this pH dependence precisely followed the pH dependence of the conduction band edge, the difference quantity ( $E_{\text{CB}} - E_f^{\text{Ru}}$ ) obviously would be pH independent. It would then likely be unnecessary to invoke sequential electron and proton transfer to account for the otherwise puzzling reaction kinetics. Candidate mechanisms for induction of pH-dependent dye energetics<sup>7</sup> could include: a) strong electronic coupling between formally metal-dye-localized electronic states and the titanium dioxide conduction band, or b) coulombic perturbation of  $E_f^{\text{Ru}}$  by surface oxide/hydroxide protonation and deprotonation processes. The former seems highly unlikely in view of the six atom (seven bond) “bridge” separating the redox-active ruthenium center from surface titanium atoms in the phosphonated dye/semiconductor assembly (eq. 1). The latter mechanism is also problematic, however, unless the primary mechanism for conduction band edge energy tuning is also coulombic perturbation (i.e. essentially a double layer effect). We have suggested elsewhere that pH-based  $E_{\text{CB}}$  tuning is instead achieved primarily via a “Pourbaix” type effect where electron addition induces the intercalation of charge-compensating cations. In any case, evaluation of the pH dependence of the formal potential for a *surface bound* dye would provide an important test of the viability of the alternative explanation of the anomalous ET rate phenomenon.

We describe below a study of the pH dependence of  $E_f$  for a representative redox dye,  $\text{Ru}(4,4'-(\text{CH}_2\text{PO}_3)-2,2'\text{-bipyridine})_3^{10-}$ , bound to a high-area titanium dioxide electrode. The study shows that the potential is approximately pH independent, supporting our original contention and supporting – at least, indirectly – the Pourbaix interpretation of conduction band edge energy modulation.

## Experimental Section

**Materials.** High-area nanocrystalline titanium dioxide electrodes were prepared in thin film form via the following procedure<sup>8</sup> which is a variant of a method described by O'Regan, et al.<sup>9</sup> Over a two minute period 30 ml of  $\text{Ti}(\text{OCH}(\text{CH}_3)_2)_4$  (Aldrich) was added dropwise to a stirring solution of nitric acid (2.6 ml) in 375 ml deionized water. Stirring was continued for 2 hours at ambient temperature, followed by 8 hours at 80° C to evaporate the propanol formed. The resulting sol was heated for an additional 12 hours at 200° C in a stainless steel pressure vessel. Water was removed by rotary evaporation until a sol concentration of 160 g/l was achieved. Carbowax 20,000 (40% weight equivalent of  $\text{TiO}_2$ ) was added to the concentrated sol and the mixture was stirred overnight. Films were prepared by spin coating the sol onto conductive glass (fluorine doped tin oxide; Asahi) followed by annealing for 1 hour in air at 400°C.

The ruthenium-based dye was prepared as a nominally hexaphosphoester species as previously described.<sup>3,10,11</sup> Conversion to the diphosphonate was accomplished by acid catalyzed hydrolysis in 6 M aq. HCl (minutes). Solvent was then removed by rotary evaporation. The dye residue was redissolved in 5 mM  $\text{HNO}_3$  in water (pH = 2.45). The surface attachment procedure consisted of soaking nanocrystalline film electrodes in the acidified dye solution for 24 hours.

$[\text{Fe}(\text{phen})_3](\text{PF}_6)_2$  (phen is 1,10-phenanthroline) was prepared by a literature method.<sup>12</sup>

**Methods.** Electrochemical measurements were initially made in a one compartment cell featuring either a titanium dioxide or indium-doped tin oxide ("conductive glass") working electrode, a platinum wire counter electrode and a saturated (NaCl) calomel reference electrode (s.s.c.e.). Potentials were controlled with a PAR 264A potentiostat. Cyclic voltammograms were recorded at 100 mV/s. Visible-region spectroelectrochemical measurements were made by using

an HP 8452A diode array spectrophotometer together with cofacial glass/conductive glass or titanium dioxide/conductive glass assemblies featuring  $\sim 100\ \mu\text{m}$  teflon spacers. In the assemblies, only the conductive glass component was employed as a working electrode component. Filling of the assemblies was achieved via capillary action. Aqueous electrolyte solutions for studies at either pH 4 or 7, respectively, contained either 50 mM potassium hydrogen phthalate or 50 mM  $\text{KH}_2\text{PO}_4$ , together with  $\text{Fe}(\text{phen})_3^{2+}$  as a redox mediator. For measurements at other pH's, appropriate amounts of  $\text{HNO}_3$  or  $\text{NaOH}$  were added. At the lowest pH's, however, the buffer component was omitted.

## Results and Discussion

Formal potentials for the surface-bound ruthenium dye were initially estimated simply by recording cyclic voltammograms. The voltammetry experiments yielded small reversible surface-type waves whose potentials were invariant with pH over the range from 1 to 8, i.e. evidence for coupling to the pH dependent conduction band energetics of the titanium dioxide electrode was not found. A point of concern, however, is that in the potential region where dye oxidation occurs the semiconductor is nominally insulating. While the observed surface redox waves could be due to leakage currents associated with mid-gap states, they conceivably also could arise from oxidation and reduction of dye molecules that interact directly with the underlying conductive glass surface (for example, via pin hole defects). In view of the typically small sizes of the waves and the correspondingly small amount of dye oxidized, the pin hole interpretation is difficult to discount. Consequently, we sought an alternative method that would enable us to determine the average potential for the entire collection of dye molecules residing on an insulating substrate.

Figure 1 illustrates the second approach. Surface bound dye molecules are indirectly addressed via interactions with a freely diffusing redox mediator,  $\text{Fe}(\text{phen})_3^{3+/2+}$ . This mediator

was chosen because of the proximity of its formal potential (0.83 V) to the anticipated dye potential. The exact potential of the dye was determined spectrally by: a) poisoning the thin-layer cell solution at a predetermined potential, b) allowing the surface-bound dye to equilibrate with the poised mediator solution, c) determining spectrally the fractions,  $f(\text{III})$  and  $f(\text{II})$ , of dye in oxidized and reduced form respectively, and d) repeating steps *a-c* at a new potential. The resulting data were then fit graphically to the Nernst equation written in the following form:<sup>13</sup>

$$E_f^{\text{Ru}} = E(\text{poised}) - (RT/F) \ln \{f(\text{III})/f(\text{II})\} \quad (2)$$

Interference from the mediator was avoided both via the offset of the mediator absorption ( $\lambda_{\text{max}} = 550 \text{ nm}$ ) from the dye absorption ( $\lambda_{\text{max}} = 460 \text{ nm}$ ) and by utilizing an extremely short solution pathlength.

Figure 2 shows a representative series of filmed-based spectral plots. Figure 3 illustrates how the resulting film absorbance varies as a function of the potential of the mediator solution. Figure 4 shows a graph based on eq. 2, where the *y* intercept provides a measure of  $E_f^{\text{Ru}}$ . Finally, Figure 5 summarizes the results of several such measurements over the pH range of 1.1 to 8.75. Attempts to extend the experiments to pH's of -1 and -4 (sulfuric acid solutions) were frustrated by decomposition of the mediator, while attempts to extend the measurements to pH = 10 were circumvented by dye desorption. Nevertheless, over the accessible solution compositional range the formal potential of the surface bound dye is essentially fully pH independent, despite demonstrated shifts in  $E_{\text{CB}}$  of ca. -450 mV over the same pH range.<sup>3,15</sup>

Coupling of  $E_f^{\text{Ru}}$  to  $E_{\text{CB}}$  would have been expected if pH-dependent variations in the latter were determined primarily by simple Coulombic effects arising from surface oxide and

hydroxide protonation and deprotonation equilibria. On the other hand, if  $E_{CB}$  were instead modulated primarily via stoichiometric proton intercalation following electron addition,<sup>6</sup> little or no coupling to  $E_f^{Ru}$  would be expected. Regardless of the expectations, however, the experimentally observed invariance of  $E_f^{Ru}$  with respect to solution pH serves to rule out the trivial “energy compensation” explanation (see introduction) for the remarkable insensitivity of previously reported<sup>3</sup> back electron transfer rates (titanium dioxide to attached Ru(III)L<sub>3</sub>) to pH-induced changes in  $E_{CB}$ .

## References

1. For recent reviews see: a) Hagfeldt, A.; Grätzel, M. *Chem. Rev.* **1995**, *95*, 49. b) Kamat, P. V. *Chem. Rev.* **1993**, *93*, 267. c) Meyer, G. J.; Searson, P. C. *Interface* **1993**, 23. d) Parkinson, B. A.; Spitler, M. T. *Electrochim. Acta* **1992**, *37*, 943.
2. Lu, H.; Prieskorn, J.; Hupp, J. T. *J. Am. Chem. Soc.* **1993**, *115*, 4927.
3. Yan, S. G.; Hupp, J. T. *J. Phys. Chem.* **1996**, *100*, 6867.
4. See also: Pechy, P.; Rotzinger, F. P.; Nazeeruddin, M. K.; Kohle, O.; Zakeeruddin, S. M.; Humphry-Baker, R.; Grätzel, M. *J. Chem. Soc., Chem. Commun.* **1995**, 65.
5. See, for example: a) Bolts, J. M.; Wrighton, M. S. *J. Phys. Chem.* **1976**, *80*, 2641. b) Watanabe, T.; Fujishima, A.; Tatsuoki, O.; Honda, K. *Bull. Chem. Soc. Jpn.* **1976**, *49*, 8.



- c) Gerischer, H. *Electrochim. Acta* **1989**, *34*, 1005. d) Hardee, K. L.; Bard, A. J. *J. Electrochem. Soc.* **1975**, *122*, 739.
6. a) Lyon, L. A.; Hupp, J. T. *J. Phys. Chem.* **1995**, *99*, 15718. b) Lemon, B. I.; Hupp, J. T. *J. Phys. Chem.* **1996**, *100*, 14578.
  7. a) Gregg, B. A., personal communication. b) Zaban, A.; Ferrere, S.; Sprague, J.; Gregg, B. A., paper submitted.
  8. Lewis, N. S.; Doig, S., personal communication.
  9. O'Regan, B.; Moser, J.; Anderson, M.; Grätzel, M. *J. Phys. Chem.* **1990**, *94*, 8720.
  10. Hirao, T.; Maunga, T.; Ohshiro, Y.; Agawa, T. *Synthesis* **1981**, 56.
  11. <sup>1</sup>H NMR characterization of a previous preparation showed evidence for hydrolysis of some of the phosphoester functionalities prior to intentional acid-catalyzed hydrolysis.<sup>3</sup>
  12. Fussa-Rydel, O.; Zhang, H-T.; Hupp, J. T.; Leidner, C. R. *Inorg. Chem.* **1989**, *28*, 1533.
  13. As expected if the spectroelectrochemical methodology were functioning reliably, the value obtained for  $E_f^{\text{Ru}}$  was unaffected by replacement of the mediator by a second mediator couple  $(\text{Fe}(5\text{-chloro-1,10-phenanthroline})_3^{2+/3+})^{12}$  displaying a different formal potential.
  14. The required  $f(\text{II})$  and  $f(\text{III})$  values were obtained from Figure 3 by assuming that  $f(\text{III})$  is unity at the most positive potential and that  $f(\text{II})$  is unity at the least positive potentials. This approach corrects for errors due to incorrect background subtraction, residual absorbance by inaccessible Ru(II) and/or residual absorbance by Ru(III).
  15. An approximately pH-invariant surface formal potential was also observed (via mediated spectroelectrochemistry) for a second complex featuring a pair of 5-nitro-1,10-phenanthroline ligands in place of 2 of the 3 available diphosphonated bipyridine ligands.

**Figure Captions**

1. Schematic depiction of thin-layer spectroelectrochemical cell and associated redox mediation scheme.
2. Dye-functionalized thin-layer cell absorbances versus a blank cell lacking the dye but containing a titanium dioxide film. Absorbance differences are shown at pH = 4 and are recorded with the mediator solution poised at 0.3 (top curve), 0.8, 0.85, 0.9, 0.95, 1.0, 1.1 and 1.3 V (bottom curve).
3. Absorbance changes at 460 nm versus poised potential of thin-layer mediator solution at pH = 4.
4. Plot of  $\log \{f(\text{III})/f(\text{II})\}$  versus poised potential of thin-layer mediator solution at pH = 4. From the y intercept,  $E_f^{\text{Ru}}$  is 0.88 V vs. s.s.c.e.
5. Plot of spectrally determined formal potential for the titanium-dioxide-immobilized ruthenium dye (see Figure 4) versus solution pH. Line drawn is a best fit line (slope = +5 mV per pH unit).

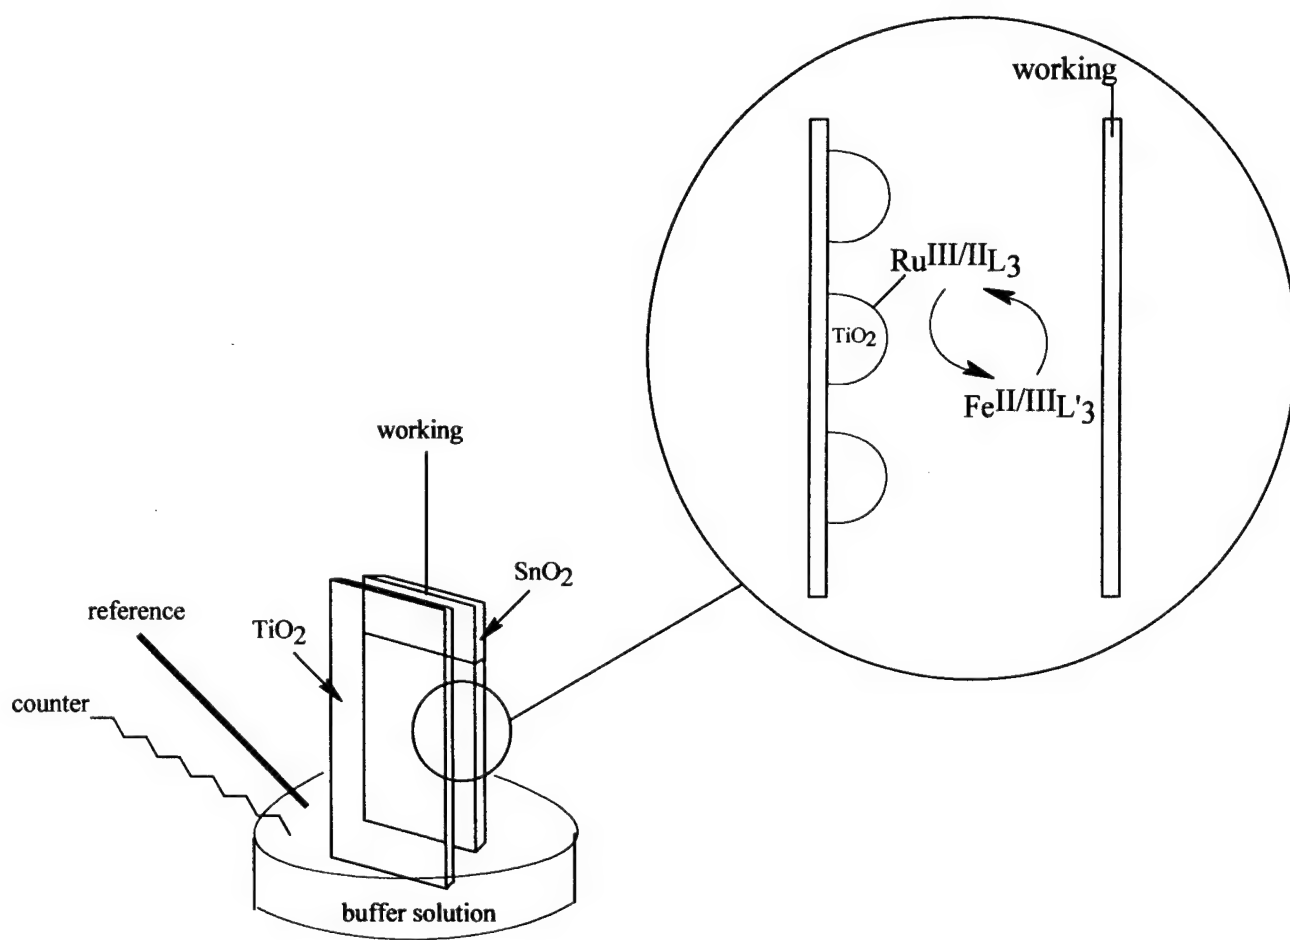


Fig. 1

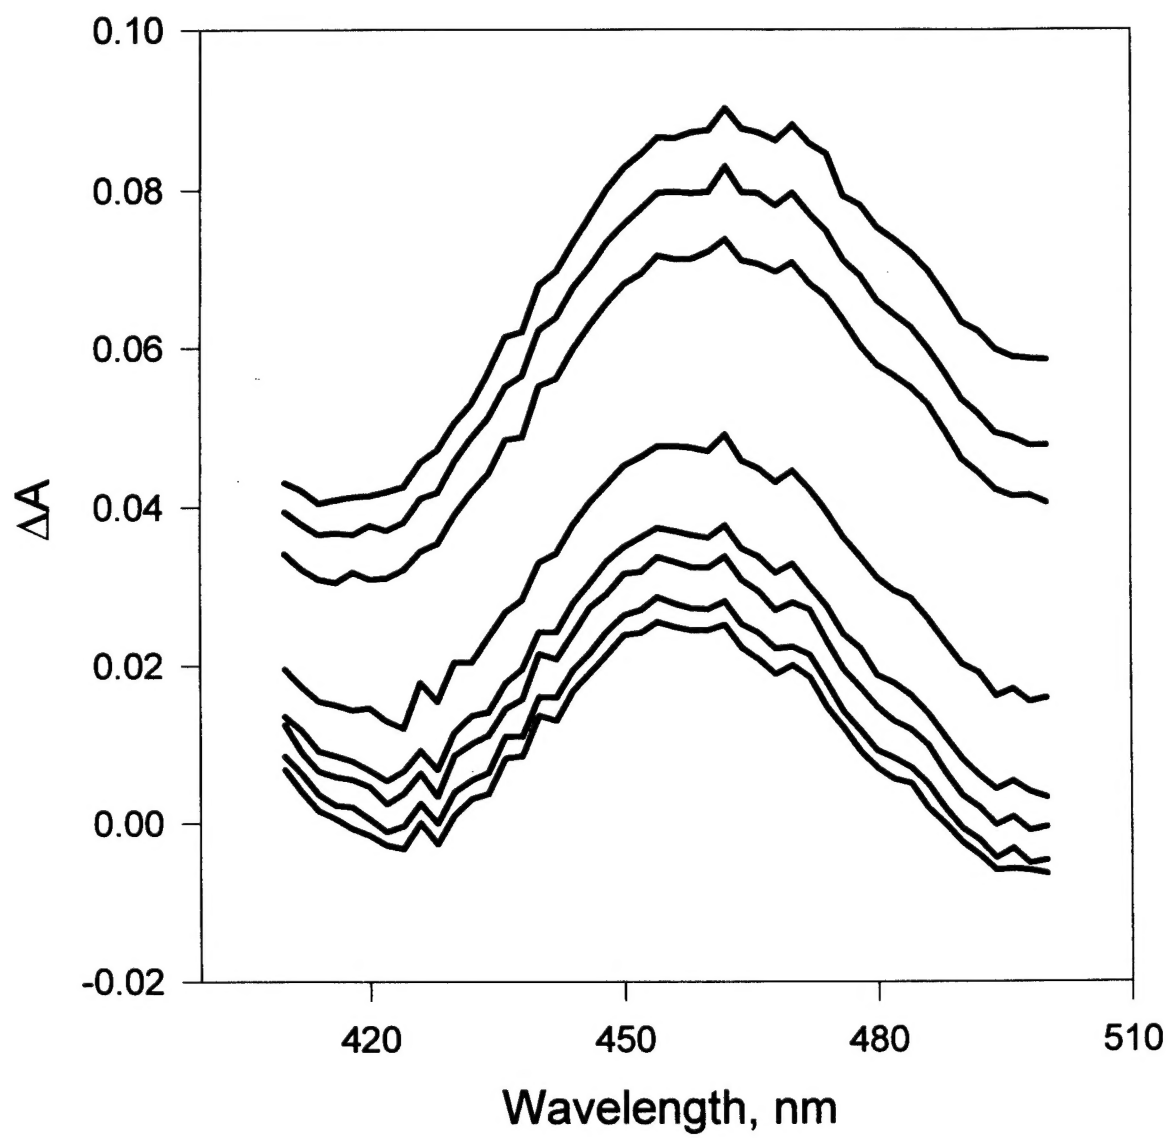


Fig. 2

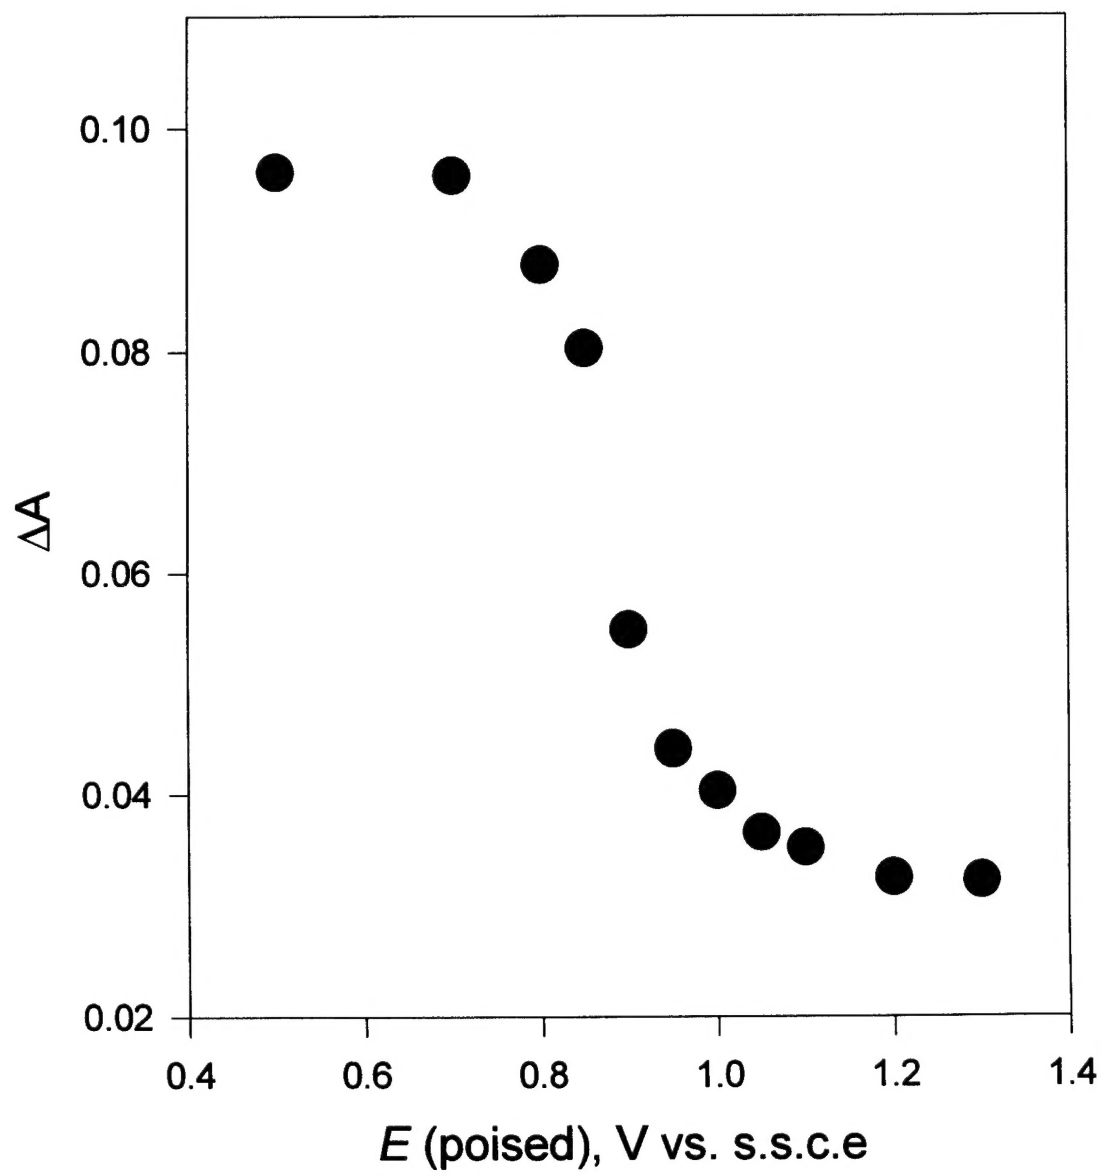


Fig.3

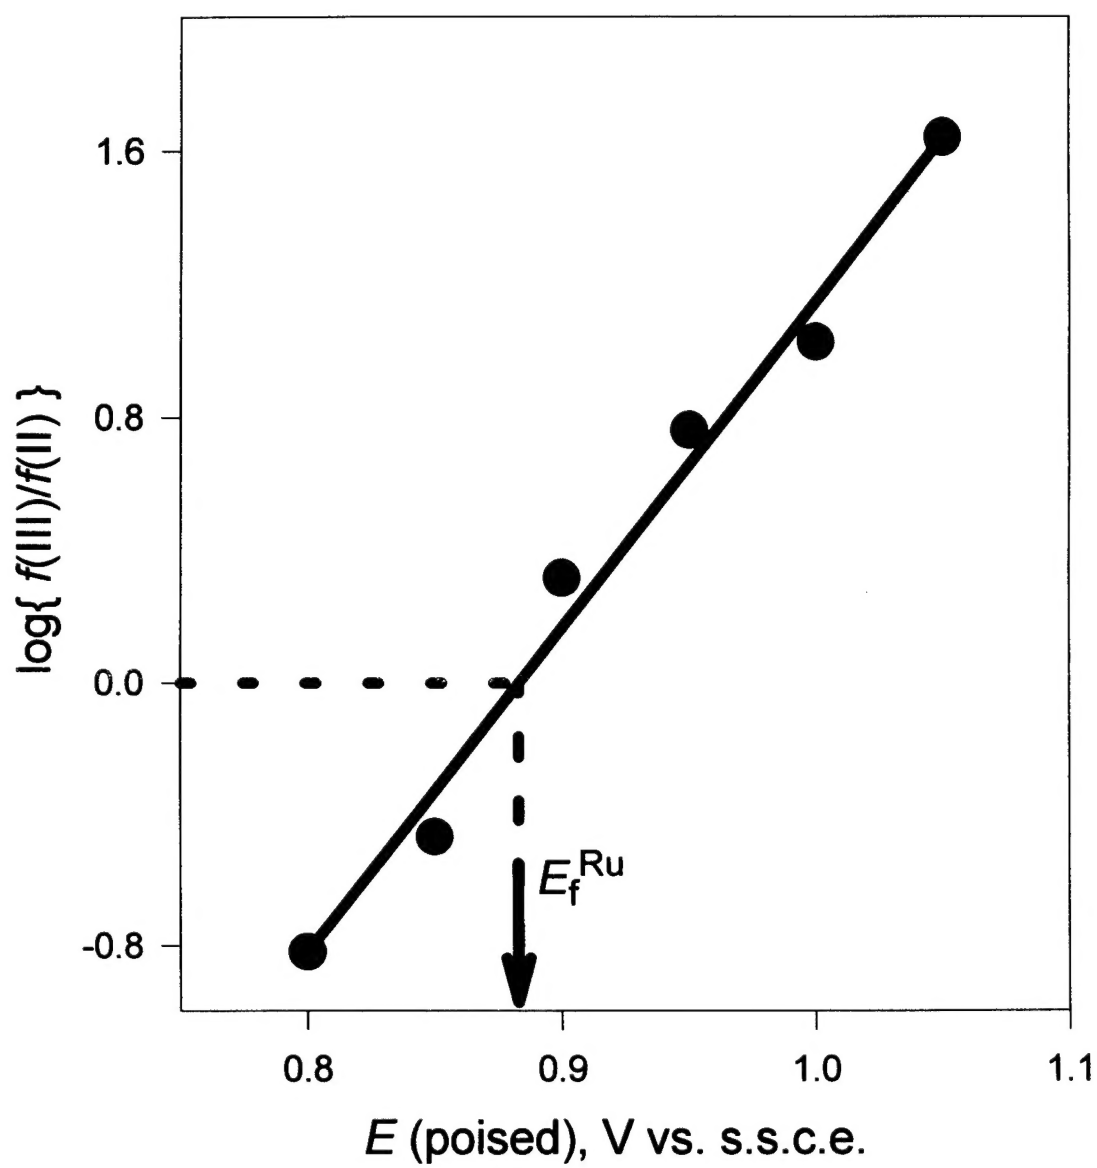


Fig. 4

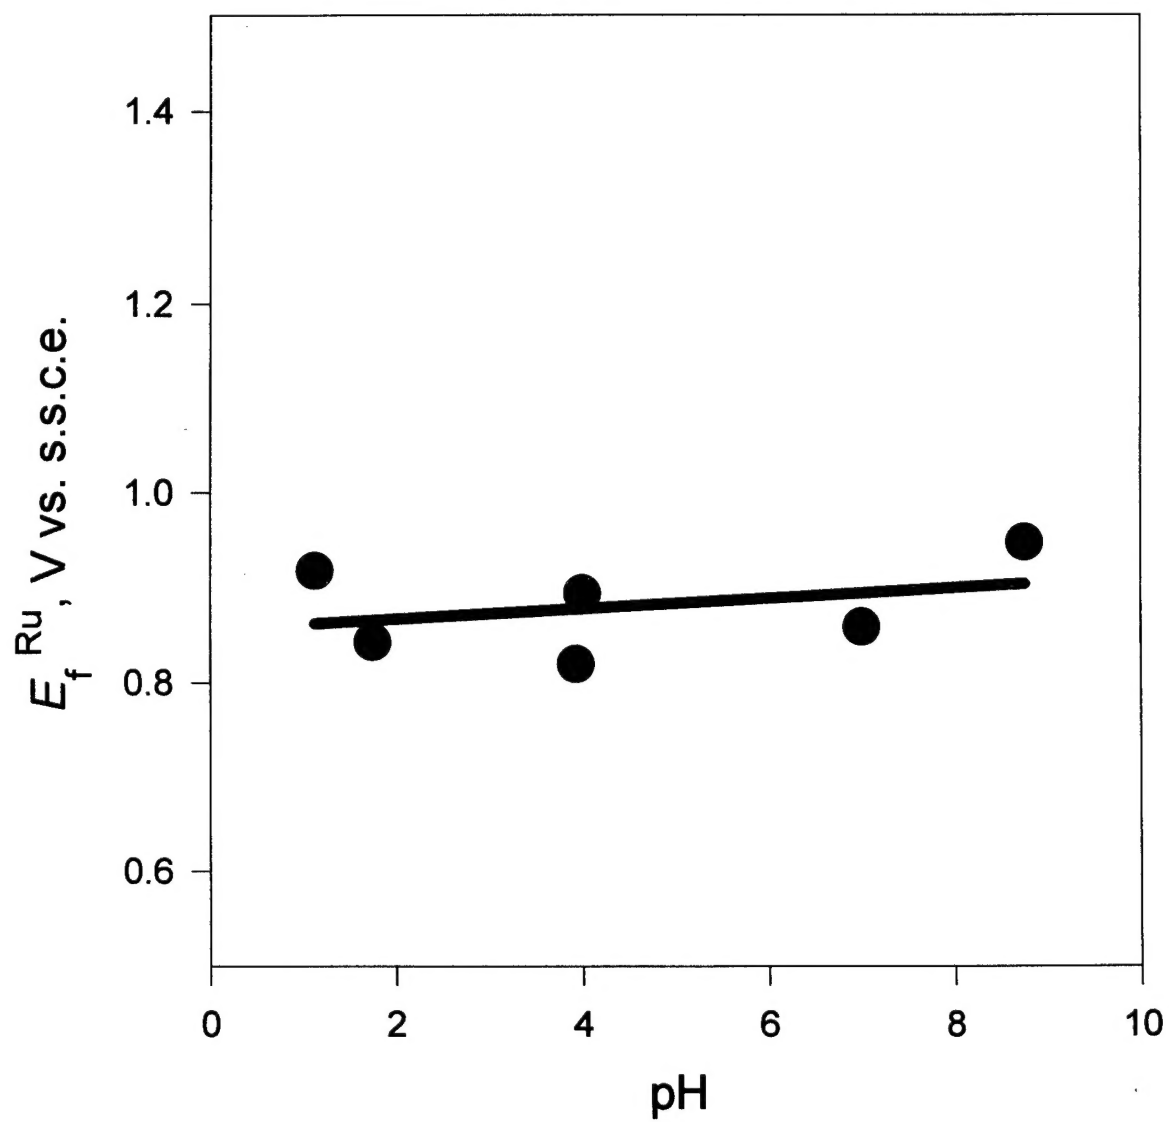


Fig. 5